

Catalytic Cracking of Palm Fatty Acid Distillate with NaOH and KOH Catalyst Supported by Gamma Alumina

Rismawati Rasyid^{1*}, Dicky Prasetyo¹, Nurul Fitriani¹, Takdir Syarif¹

¹Departement of Chemical Engineering, Faculty of Industrial Technology, Universitas Muslim Indonesia, Makassar, Indonesia

Abstract. This article describe about the study of produce fuel from palm fatty acid distillate with a similar composition to fossil fuels through catalytic cracking method using alkaline heterogeneous catalyst. The catalytic cracking reaction was operated at batch reactor with a constant temperature of 370°C, a volume of 50 mL of feedstock, a pressure of 1 atm, and two kinds of catalysts: NaOH/ γ -Al₂O₃ and KOH/ γ -Al₂O₃ which has been characterization with X-ray diffraction and scanning electron microscopy. The best catalyst to produce biofuel type biogasoline (C₅-C₁₅) is KOH/ γ -Al₂O₃ (5%) with a yield of 70% and selectivity to biogasoline of 74.46%. Meanwhile, the best catalyst to produce biofuel type biodiesel (C₁₅-C₂₂) is NaOH/ γ -Al₂O₃ (5%) with a yield of 80% and selectivity to biodiesel of 67.72%.

Keywords: Biodiesel; Biogasoline; Catalytic Cracking; Palm fatty acid distillate

1. Introduction

The depletion of fossil fuels, coupled with the rapid growth in living standards, has led to a significant increase in fuel prices and the subsequent impact on greenhouse gas emissions. This has prompted researchers to prioritize the development of renewable and non-polluting fuels, which hold the promise of achieving global energy security while also mitigating the effects of climate change (Ibrahim, *et al.*, 2020; Singh *et al.*, 2020; Wakoc, *et al.*, 2018). Palm oils are widely considered to be the most promising feedstock for the production of such alternative fuels, known colloquially as biofuels. Nevertheless, if palm oil is used as a raw resource for biofuels for an extended period, it will eventually compete with foodstuffs. Using byproducts of palm oil processing, which still contain a lot of fatty acids as a raw material is a very wise decision (Oliveira, *et al.*, 2021; Arita *et al.*, 2020; Onlamnao and Tippayawong, 2020; Zaher, *et al.*, 2017).

Among all biofuel preparation technologies, catalytic cracking is considered a promising method due to its simple process which can be carried out at atmospheric pressure, has a higher cracking conversion efficiency, higher light alkene selectivity, less carbon deposition and the production of several types of liquid products similar to petroleum-based fuels. Furthermore, with appropriate catalysts, catalytic cracking can be used to produce gasoline, kerosene, and diesel, and it has good compatibility with various feedstocks as well as a lower cost (Ulfiati *et al.*, 2022; Zhang, *et al.*, 2021; Orazbayev, *et al.*,

*Corresponding author's email: rismawati.rasyid@umi.ac.id, Tel.: +62411455666
doi: [10.14716/ijtech.v15i3.5980](https://doi.org/10.14716/ijtech.v15i3.5980)

2020; Nieuwelink *et al.*, 2020; Singh *et al.*, 2020; Mammadova *et al.*, 2018). The cracking reaction is characterized primarily by a break in the "carbon-carbon" bond, indicating an endothermic reaction—the higher the temperature, the faster the reaction (Wang *et al.*, 2019). In comparison to the transesterification process, the catalytic cracking process is a more efficient method that offers greater flexibility in product output. The transesterification process, on the other hand, involves several complex steps, including the separation of products and by-products and the initial treatment of high FFA to prevent saponification reactions. Additionally, this process produces only one type of biofuel, and the production time can be relatively long, with processing times of around 5 hours and purification times of up to 24 hours (Wahyono *et al.*, 2022; Rasyid *et al.*, 2018). Meanwhile, when compared to the hydrocracking process, which requires high temperatures 350°C and 29.6077 atm pressures, the catalytic cracking process is more cost-effective because it can be operated at lower temperatures and atmospheric pressure (Trisunaryanti *et al.*, 2020; Al-Muttaqi *et al.*, 2019; Rasyid *et al.*, 2015).

Currently, to meet the requirements of vehicle fuel standards, catalytic cracking must reduce the acid value and oxygen content of the biofuel which are biogasoline (C₅-C₁₅) dan biodiesel (C₁₆-C₂₂) to improve fuel properties such as density, calorific value, dynamic viscosity, and other parameters (Sardi *et al.*, 2022; Makertihartha *et al.*, 2020). There is no doubt that catalysts play an important role in the catalytic cracking of fatty acids to produce biofuel. Alkaline catalysts such as sodium hydroxide (NaOH) and potassium hydroxide (KOH) are commonly used in the production of biofuels because their rate of reaction is much faster than that of acid catalysts (Min *et al.*, 2015). High catalytic activity, shorter reaction time, simple operating conditions, low cost, and availability are just a few of the advantages of NaOH and KOH catalysts. However, homogeneous base catalysts, on the other hand, are extremely sensitive to free fatty acids and water. Therefore, a homogeneous catalyst was modified into a heterogeneous catalyst by the addition of a catalyst support (Widayat *et al.*, 2016).

Heterogeneous catalysts can be designed to graft and trap active molecules on the surface or within the pores of solid supports such as silica, alumina, or CaO (Thangaraj *et al.*, 2019). Gamma alumina (γ -Al₂O₃) is used as a catalyst support because it has a large surface area (150-300 m²/g) and an amphoteric acid and base active site with various strengths depending on the method of production. Furthermore, γ -Al₂O₃ serves the primary function of providing surface area for the active component, with the purpose of increasing contact between the active core and the reactants while maintaining active phase activity (Rasyid *et al.*, 2018). The presence of acid sites on Al₂O₃, which are associated with Lewis acidity and very weak Brønsted acidity, makes it an effective catalyst for deoxygenation with minimal aromatization (Istadi *et al.*, 2021). Thus, making heterogeneous NaOH/ γ -Al₂O₃ and KOH/ γ -Al₂O₃ catalysts may be a feasible method to integrate the required acidic and basic characteristics to overcome defects in NaOH and KOH catalysts and avoid an excessive production of aromatic hydrocarbons by acid solid catalysts (Zheng *et al.*, 2019).

Therefore, the catalytic cracking of palm fatty acid distillate for biofuels was carried out using heterogeneous NaOH/ γ -Al₂O₃ and KOH/ γ -Al₂O₃ catalysts. Mechanically, NaOH/ γ -Al₂O₃ and KOH/ γ -Al₂O₃ catalysts were created by combining NaOH and KOH as primary catalysts and γ -Al₂O₃ as catalysts support. This research aims to produce a fuel with a similar composition to fossil fuels.

2. Methods

2.1. Tools

The main tool in this research is a catalytic cracking reactor with supporting components (Figure 1).

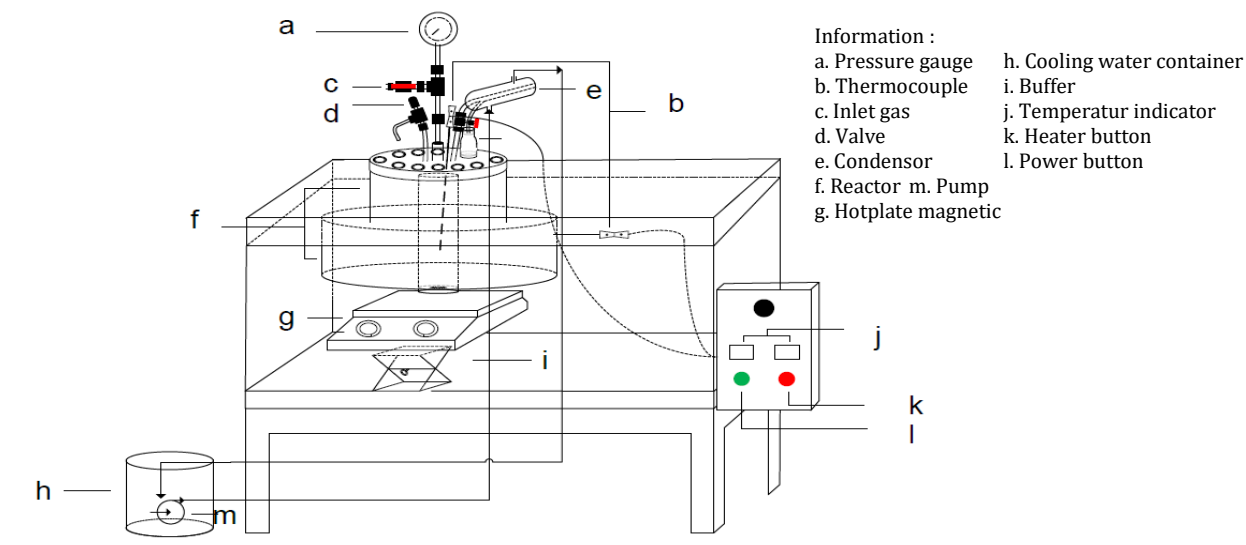


Figure 1 Catalytic Cracking Reactor

2.2. Preparation of Catalysts

The catalyst was prepared from sodium hydroxide (NaOH) p.a merck and potassium hydroxide (KOH) p.a merck as catalyst site active element which impregnated into support gamma alumina ($\gamma\text{-Al}_2\text{O}_3$) from merck (p.a). Wet impregnation was used to prepare the catalysts. NaOH 0.5 N was impregnated into 10 grams of $\gamma\text{-Al}_2\text{O}_3$ to prepare NaOH/ $\gamma\text{-Al}_2\text{O}_3$ catalyst, then it was stirred with a magnetic hotplate stirrer while the water in the mixture evaporated to form a paste. The mixture of the catalysts would be dried at 110°C within 8 hours. Afterward, the mixture was calcined for 3 hours at a temperature of 500°C. Furthermore, the same process was carried out with KOH 0.5 N to preparation KOH/ $\gamma\text{-Al}_2\text{O}_3$ catalyst.

2.3. Catalytic Cracking Process

A batch reactor with a pressure of 1 atm was used to conduct the reaction. The reactor is filled with 50 mL of palm fatty acid distillate from palm oil refining, 0.5 grams of NaOH/ $\gamma\text{-Al}_2\text{O}_3$ catalyst (1% of the raw ingredients), and a magnetic stirrer. The reaction is then performed for two hours after the reactor heater is turned on until it reaches a temperature of 370°C (Aziz *et al.*, 2020). The biofuel product will evaporate from the reactor to the liquid product container during the reaction and flow through the condenser. Remaining in the reactor is the residue, and the amount of gaseous product that hasn't condensed is estimated using the mass balance equation by deducting the initial amount of raw material from the final product. Furthermore, the catalytic cracking process is carried out with a NaOH/ $\gamma\text{-Al}_2\text{O}_3$ catalyst (3, 5, 7)% and KOH/ $\gamma\text{-Al}_2\text{O}_3$ catalyst (1, 3, 5, 7)%.

The yield product calculations and GC-MS analysis were carried out to determine the selectivity of the catalyst for biofuel products. The results of product yield and selectivity are obtained from equations (1) and (2).

$$\text{Yield} = \frac{\text{Product Volume (mL)}}{\text{Palm Oil Volume (mL)}} \times 100 \% \quad (1)$$

$$\text{Selectivity} = \frac{\text{Selected product area}}{\text{The total area of all products}} \times 100\% \quad (2)$$

2.4. Product Analysis

- Scanning Electron Microscopy (SEM) and X-Ray Diffraction (XRD) at the following conditions: 40 KV, 15 mA, CuK/1.54060 Time/step of 23.9700 s, step size of 0.0220 deg, and Scan axis Gonio were used to characterize the catalyst.
- Gas chromatography-mass spectrometry (GC-MS) with an Agilent capillary number of 19.091 S-493, HP-5MS of 5% phenyl methyl siloxane, nominal length of 30.0 m, nominal diameter of 250 μm , nominal film thickness of 0.25 μm , and nominal initial pressure of 10.5 psi was used to analyze the product's component compounds.

3. Results and Discussion

3.1. Characterization of NaOH/ $\gamma\text{-Al}_2\text{O}_3$ and KOH/ $\gamma\text{-Al}_2\text{O}_3$ Catalyst

3.1.1 X-Ray Diffraction (XRD) Analysis

X-ray Diffraction (XRD) was used to identify content that was impregnated on the support of catalyst ($\gamma\text{-Al}_2\text{O}_3$) as the NaOH/ $\gamma\text{-Al}_2\text{O}_3$ and KOH/ $\gamma\text{-Al}_2\text{O}_3$ catalysts (Figure 2).

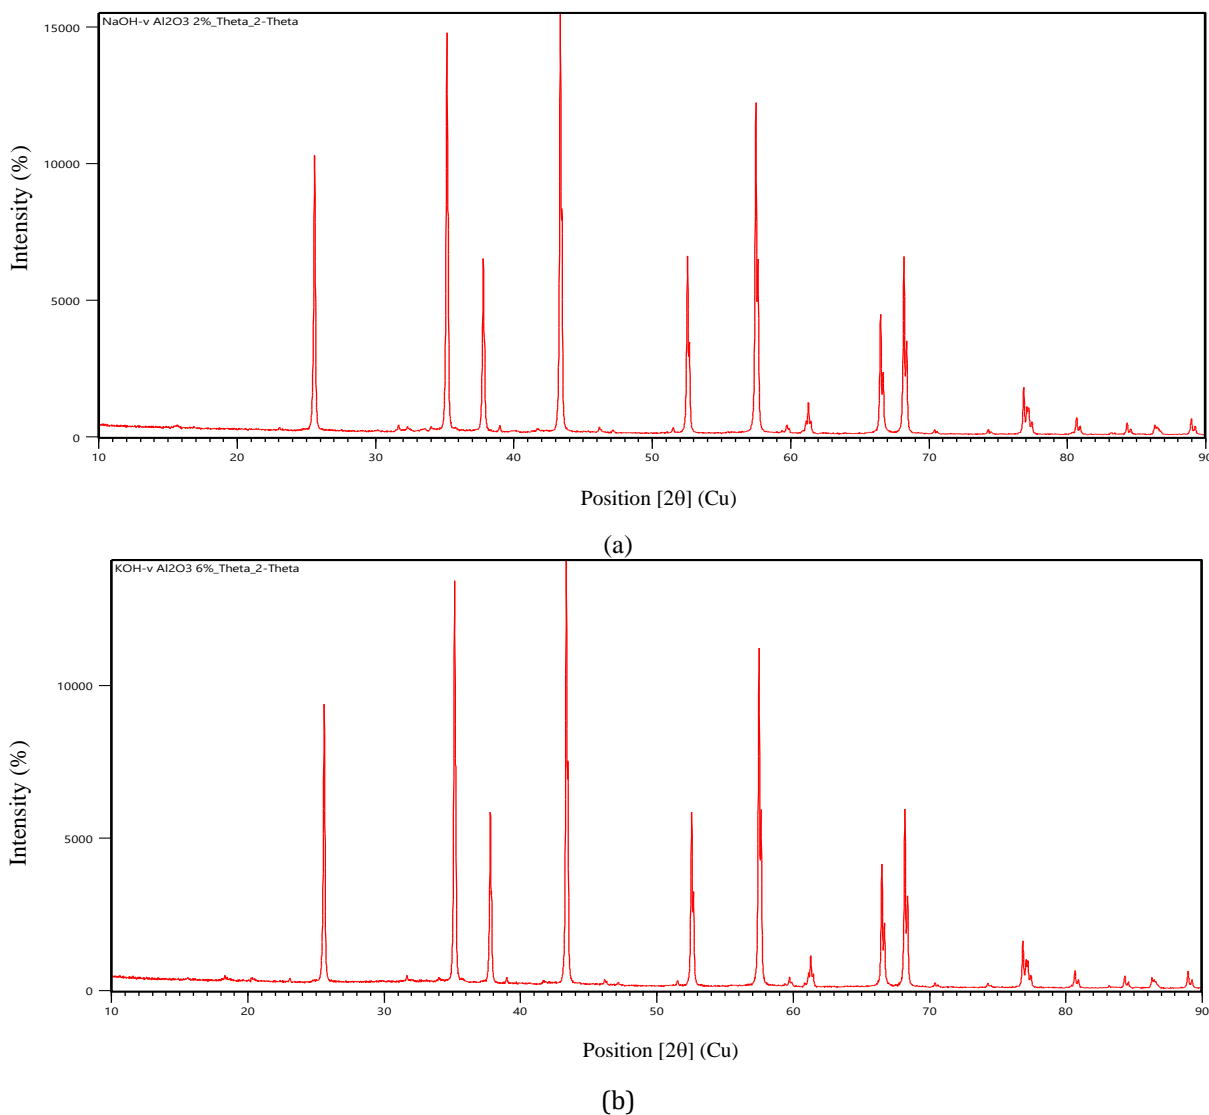


Figure 2 XRD diffractogram (a) NaOH/ $\gamma\text{-Al}_2\text{O}_3$ catalyst, and (b) KOH/ $\gamma\text{-Al}_2\text{O}_3$ catalysts

According to ICDD (International Center for Diffraction Data) 00-010-0425, Gamma Alumina ($\gamma\text{-Al}_2\text{O}_3$) has peaks at $2\theta = 37^\circ, 39^\circ, 45^\circ,$ and 67° . As shown in Figure 2, NaOH/ $\gamma\text{-Al}_2\text{O}_3$ has peaks 2θ that are similar to $\gamma\text{-Al}_2\text{O}_3$, such as $37^\circ, 39^\circ,$ and 67° , but there are new peaks formed due to impregnation, indicating the presence of deposited NaOH catalyst. Likewise, the KOH/ $\gamma\text{-Al}_2\text{O}_3$ catalyst has peaks 2θ that are similar to $\gamma\text{-Al}_2\text{O}_3$, notably $37^\circ, 39^\circ,$ and 67° , and there are new peaks are formed due to impregnation, proving the presence of deposited KOH catalyst (Singh *et al.*, 2020; Yu *et al.*, 2019; Wako *et al.*, 2018).

3.1.2 Scanning Electron Microscopy (SEM) Analysis

A SEM analysis was conducted to determine the surface morphology of the catalyst before and after impregnation of the active site of the catalyst. SEM analysis of the catalyst was carried out at a magnification of $10\ \mu\text{m}$ (Figure 3).

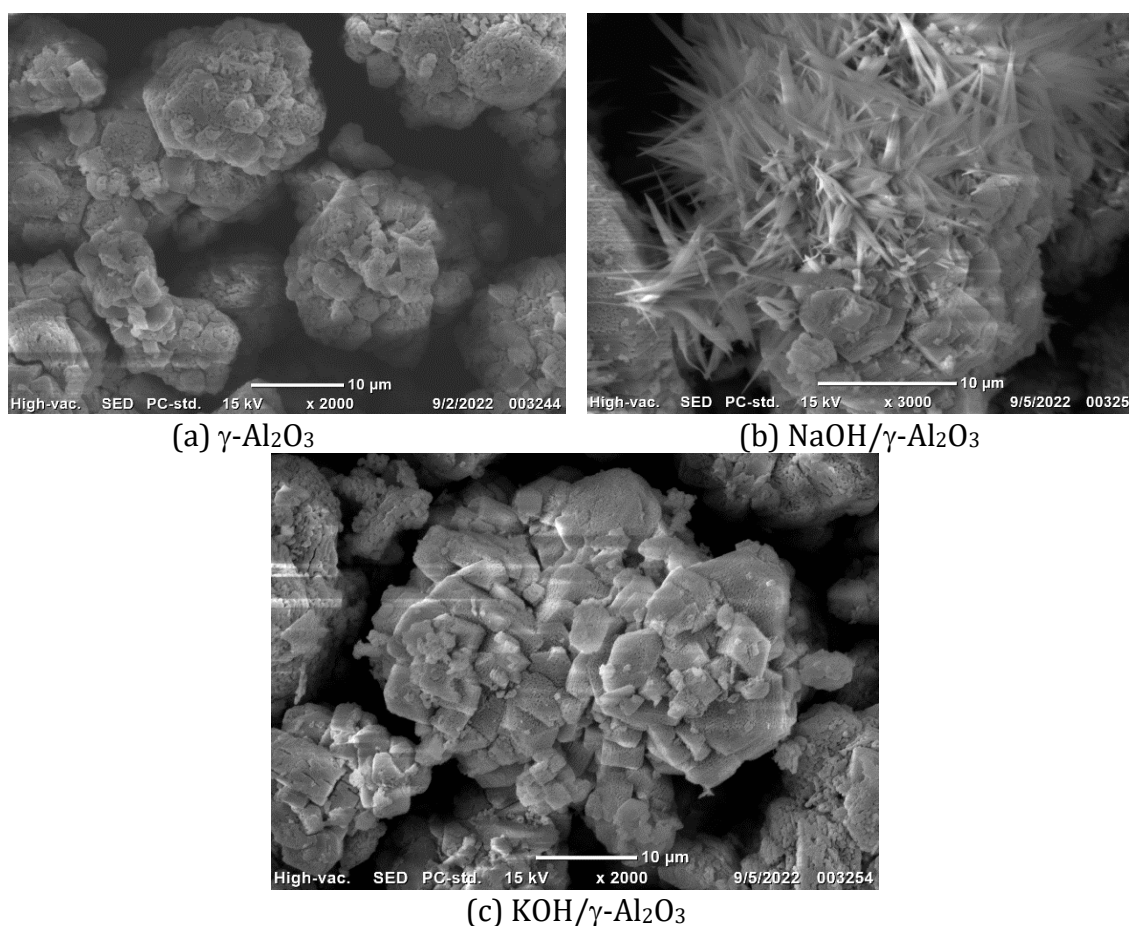


Figure 3 Surface Morphology of: (a) $\gamma\text{-Al}_2\text{O}_3$; (b) NaOH/ $\gamma\text{-Al}_2\text{O}_3$; and (c) KOH/ $\gamma\text{-Al}_2\text{O}_3$ catalysts

The surface morphology of the catalyst support ($\gamma\text{-Al}_2\text{O}_3$) revealed a regular crystal structure before impregnation, whereas after impregnation revealed that the impregnated active site had attached and distributed to the support's main structure.

3.2. Gas Chromatography-Mass Spectrometry Analysis of Palm Fatty Acid Distillate

Palm fatty acid distillate was GC-MS analyzed before the catalytic cracking process to determine the compound composition of the raw material used (Table 1). The by-product of palm oil processing used in this study still contains triglyceride components, specifically free fatty acids. As noted by (Oliveira *et al.*, 2021), the conversion of palm oil into cooking oil can result in up to 6% of the by-product of feed CPO being left behind. The byproduct is palm oil fatty acid distillate, which contains a high concentration of free fatty acids. There

are also significant amounts of hydrocarbon compounds (Table 1). This shows that palm oil waste has the potential to be used as a raw material in the production of biofuels.

Table 1 The Compound Composition of Palm Fatty Acid Distillate

| Chemical Formula | Composition(%) | Chemical Formula | Composition(%) |
|---|----------------|--|----------------|
| C ₃ H ₄ N ₂ O | 0.27 | C ₁₁ H ₂₂ O ₂ | 0.39 |
| C ₃ H ₆ N ₄ O ₃ | 0.35 | C ₁₁ H ₂₃ O ₂ | 1.60 |
| C ₅ H ₈ O ₂ | 0.24 | C ₁₁ H ₂₄ | 1.07 |
| C ₅ H ₁₀ O | 0.63 | C ₁₁ H ₁₀ | 1.86 |
| C ₆ H ₁₂ | 2.35 | C ₁₂ H ₂₆ | 14.77 |
| C ₆ H ₁₀ O ₂ | 1.73 | C ₁₂ H ₂₄ | 4.15 |
| C ₇ H ₁₆ | 2.84 | C ₁₂ H ₁₈ O | 0.93 |
| C ₇ H ₁₀ | 0.30 | C ₁₂ H ₂₆ O | 0.31 |
| C ₇ H ₁₀ O ₂ | 2.26 | C ₁₃ H ₂₈ | 12.99 |
| C ₇ H ₁₆ O | 4.22 | C ₁₄ H ₂₈ | 2.58 |
| C ₈ H ₁₈ | 0.64 | C ₁₅ H ₃₀ | 2.4 |
| C ₈ H ₁₆ | 2.11 | C ₁₆ H ₃₀ | 1.17 |
| C ₈ H ₁₅ N ₃ O | 1.39 | C ₁₈ H ₃₄ O ₂ | 1.01 |
| C ₉ H ₁₈ O | 0.83 | C ₁₈ H ₃₆ O ₂ | 6.38 |
| C ₉ H ₁₆ | 1.96 | C ₁₉ H ₃₀ O | 1.99 |
| C ₁₀ H ₈ | 2.66 | C ₂₀ H ₂₀ O ₄ | 1.78 |
| C ₁₀ H ₁₆ O | 0.2 | C ₂₀ H ₃₆ O ₂ | 2.08 |
| C ₁₀ H ₁₈ O | 0.79 | C ₂₆ H ₃₄ O ₁₀ | 1.19 |
| C ₁₀ H ₂₂ | 0.28 | C ₂₈ H ₃₄ N ₂ O | 1.13 |
| C ₁₀ H ₂₂ | 9.48 | C ₃₆ H ₇₄ | 2.84 |
| C ₁₀ H ₁₄ O ₂ | 0.23 | CH ₄ N ₂ O | 0.77 |

3.3. Product Yield Analysis Results

Biofuel products are obtained from the catalytic cracking process in the form of liquid and gas, and also residues, which are raw materials that are not cracked. The liquid and gas results are added up and then calculated using equation (1) to determine the yield of each reaction.

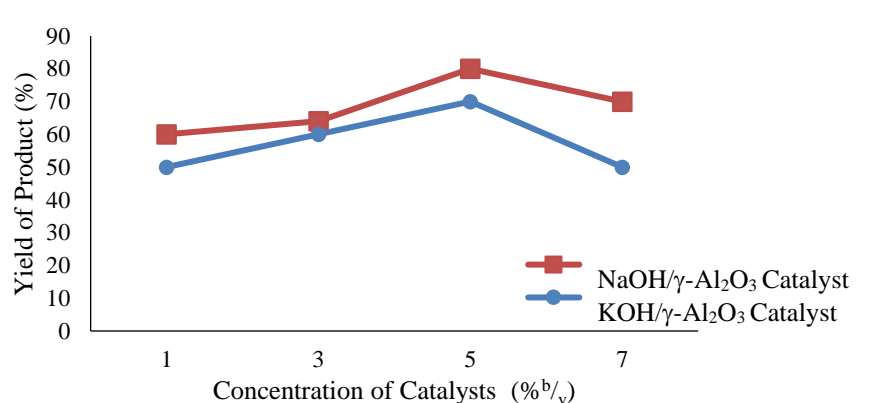


Figure 4 Graph of the Relationship between Concentration of Catalysts and Yield Product

The yield of the product obtained in the biofuel production process by catalytic cracking of palm fatty acid distillate with NaOH/ γ -Al₂O₃ and KOH/ γ -Al₂O₃ catalysts was directly proportional to the catalyst concentration up to 5% and experienced product yields at 7% catalyst concentration (Figure 4). Studies by (Thambiyapillaia and Ramanujam, 2021; Akah, Williams, and Ghrami, 2019; Prabasari, *et al.*, 2019) have demonstrated that the addition of a catalyst to a catalytic cracking reaction can increase the reaction rate, resulting in higher yields. However, it is important to note that if the catalyst's performance has already reached its optimum limit, adding more of it beyond that point will not lead to further improvements in the reaction's effectiveness

Despite the similarities in the line chart, the amount of yield produced by each catalyst is different. The yield obtained with the NaOH/ γ -Al₂O₃ catalyst was greater than the yield obtained with the KOH/ γ -Al₂O₃ catalyst. The product yield obtained with the NaOH/ γ -Al₂O₃ (5%) catalyst was 80% while the higher yield of KOH/ γ -Al₂O₃ (5%) was 70%. This is due to the active site distribution of the NaOH/ γ -Al₂O₃ catalyst obtained through scanning electron microscopy analysis appearing wider and adhering more to the catalyst support (Figure 3).

3.3. Selectivity Product

The biofuel product produced through the cracking process of palm fatty acid distillate using a NaOH/ γ -Al₂O₃ catalyst and a KOH/ γ -Al₂O₃ catalyst contains various hydrocarbon compounds, so gas chromatography-mass spectrometry analysis is carried out. Biofuels are classified based on their constituent hydrocarbon chains, which are biogasoline (C₅-C₁₅) dan biodiesel (C₁₆-C₂₂) (Aziz *et al.*, 2021a ; Onlamnao and Tippayawong, 2020; Ibarra *et al.*, 2019). Then calculate the selectivity of the catalyst for the type of biofuel produced by using equation (2).

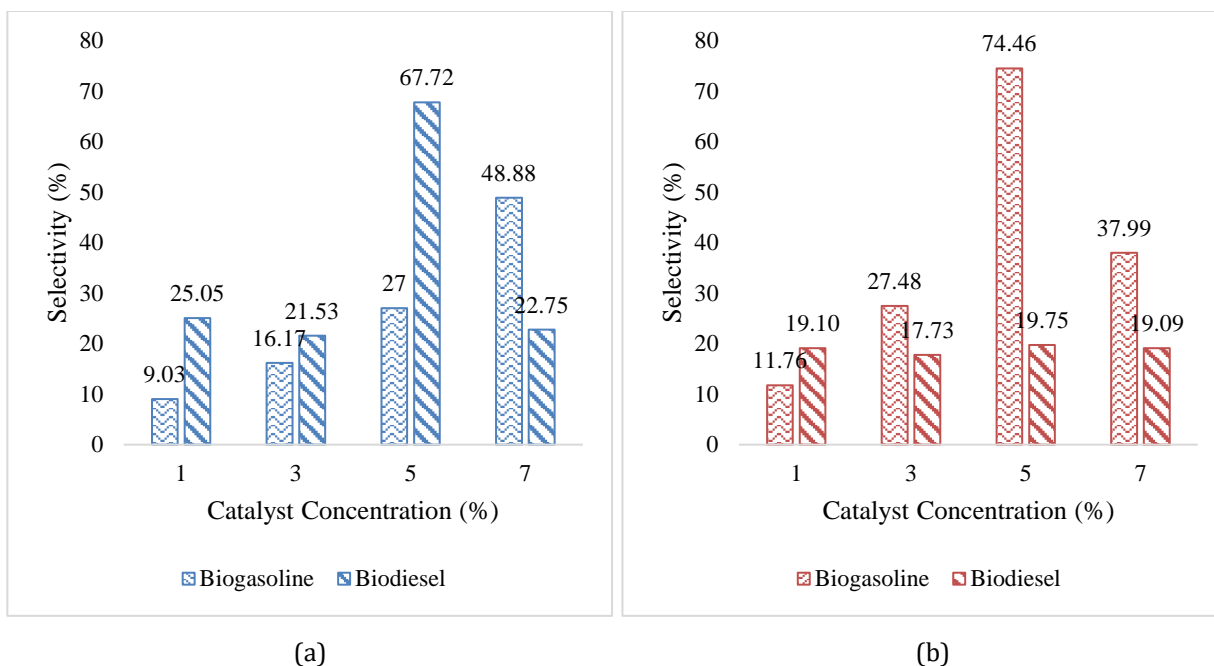


Figure 5 Graph of Relationship between Catalyst Mass and Selectivity of Biofuel Products using a catalyst (a) NaOH/ γ -Al₂O₃; and (b) KOH/ γ -Al₂O₃ catalysts

The highest conversion of biodiesel product from the catalytic cracking of palm fatty acid distillate was obtained with NaOH/ γ -Al₂O₃ (5%) catalyst, which was 67.72%. This shows that the NaOH/ γ -Al₂O₃ catalyst is more selective towards long-chain biofuels (C₁₅-C₂₂) compared to the KOH/ γ -Al₂O₃ catalyst, which produces less than 20% biodiesel.

Meanwhile, the conversion of biogasoline products from the catalytic cracking of palm fatty acid distillates with the NaOH/ γ -Al₂O₃ catalyst shows data that is directly proportional to the increase in the catalyst. The highest biogasoline product with NaOH/ γ -Al₂O₃ catalyst was obtained at 7% catalyst, which was 48.88%, indicating that if the catalyst is increased again, the conversion may increase or decrease. However, when compared to the catalytic cracking of palm fatty acid distillate with a KOH/ γ -Al₂O₃ catalyst, better results were obtained, where the optimum biogasoline production point was obtained with a KOH/ γ -Al₂O₃ catalyst (5%) and a bio gasoline yield of 74.46%. This shows that the KOH/ γ -Al₂O₃ catalyst is more selective towards short-chain biofuels (C₅-C₁₅) than the NaOH/ γ -Al₂O₃

catalyst. According to (Aziz *et al.*, 2021b; Istadi *et al.*, 2021; Senter *et al.*, 2021), catalysts that produce short-chain biofuels have high performance. The product's selectivity is proportional to the Lewis to Brønsted ratio (L/B ratio). When the L/B ratio is high, the Lewis acid site is dominant. Because of the catalyst's low L/B ratio, the NaOH/ γ -Al₂O₃ catalyst promotes the formation of long chains (biodiesel).

4. Conclusions

Palm fatty acid distillate (PFAD) can be converted into biogasoline (C5–C15) and biodiesel (C16–C22) at a pressure of 1 atm using NaOH/ γ -Al₂O₃ and KOH/ γ -Al₂O₃ as catalysts in a catalytic cracking process. KOH/ γ -Al₂O₃ (5%) is the best catalyst for producing biofuel type biogasoline (C5–C15), with a yield of 70% and a selectivity to biogasoline of 74.46%. Meanwhile, the best catalyst for producing biofuel type biodiesel (C15–C22) is NaOH/ γ -Al₂O₃ (5%), which has an 80% yield and a 67.72% selectivity for biodiesel. Furthermore, the product of this research can be utilized as a blend of commercial fuels, given that they contain the same compounds and that the combustion products are easily decomposed, minimizing pollution to the environment. It is also intended to reduce the use of fossil fuels, ensuring global energy availability. This research can be expanded with different pre-treatments in the manufacture of catalysts to increase their effectiveness, as well as the addition of appropriate promoters.

Acknowledgments

DRPM KEMENDIKBUDRISTEK for assistance with funding in the PTUPT research scheme (Number : 2327.I/B.07/UMI/VII/2022). The academic community of Fakultas Teknologi Industri Universitas Muslim Indonesia, where the research is held at the Chemical Engineering Process Laboratory.

References

- Akah, A., Williams, J., Ghrami, M., 2019. An Overview of Light Olefins Production via Steam Enhanced Catalytic Cracking. *Catalysis Surveys from Asia*, Volume 23, pp. 265–276
- Al-Muttaqi, M., Kurniawansyah, F., Prajitno, D.H., Roesyadi, A., 2019. Hydrocarbon Biofuel Production by Hydrocracking Process with Nickel-Iron Supported on HZSM-5 Catalyst. *In: IOP Conference Series: Materials Science and Engineering*, Volume 543(1), p. 012055
- Arita, S., Nazarudin, N., Rosmawati, R., Komariah, L.N., Alfernando, O., 2020. The Effect of Combined H-USY and ZSM-5 Catalyst in Catalytic Cracking of Waste Cooking Oil to Produce Biofuel. *In: AIP Conference Proceedings*, Volume 2242(1), p. 040047
- Aziz, I., Ardine, E.A.F., Saridewi, N., Adhani, L., 2021a. Catalytic Cracking of Crude Biodiesel into Biohydrocarbon Using Natural Zeolite Impregnated Nickel Oxide Catalyst. *Jurnal Kimia Sains dan Aplikasi*, Volume 24(7), pp. 222–227
- Aziz, I., Kurnianti, Y., Saridewi, N., Adhani, L., Permata, W., 2020. Utilization of Coconut Shell as Cr₂O₃ Catalyst Support for Catalytic Cracking of Jatropha Oil into Biofuel. *Jurnal Kimia Sains dan Aplikasi*, Volume 23(2), pp. 39–45
- Aziz, I., Retnaningsih, T., Gustama, D., Saridewi, N., Adhani, L., Dwiatmoko, A.A., 2021b. Catalytic Cracking of Jatropha Oil into Biofuel over Hierarchical Zeolite Supported NiMo Catalyst. *In: AIP Conference Proceedings*, Volume 2349(1), p. 020004
- Ibarra, Á., Hita, I., Azkoiti, M.J., Arandes, J.M., Bilbao, J., 2019. Catalytic Cracking of Raw Bio-oil under FCC Unit Conditions over Different Zeolite-based Catalysts. *Journal of Industrial and Engineering Chemistry*, Volume 78, pp. 372–382

- Ibrahim, H., Silitonga, A.S., Rahmawaty, Dharma, S., Sebayang, A.H., Khairil., Sumartono, Sutrisno, J., Razak, A., 2020. An Ultrasound Assisted Transesterification to Optimize Biodiesel Production from Rice Bran Oil. *International Journal of Technology*, Volume 11(2), pp. 225–234
- Istadi, I., Riyanto, T., Buchori, L., Anggoro, D.D., Pakpahan, A.W., Pakpahan, A.J., 2021. Biofuels Production from Catalytic Cracking of Palm Oil Using Modified HY Zeolite Catalysts over A Continuous Fixed Bed Catalytic Reactor. *International Journal of Renewable Energy Development*, Volume 10(1), pp. 149–156
- Makertihartha, I.G.B., Fitriadi, R.B., Ramadhani, A.R., Laniwati, M., Muraza, O., Subagjo, 2020. Biogasoline Production from Palm Oil: Optimization of Catalytic Cracking Parameters. *Arabian Journal for Science and Engineering*, Volume 45, pp. 7257–7266
- Mammadova, T., Abbasov, M., Movsumov, N., Latifova, T., Hasanova, A., Kocharli, Z., Irada, K., Abbasov, V., 2018. Production of Diesel Fractions by Catalytic Cracking of Vacuum Gas Oil and Its mixture with Cottonseed Oil under the influence of a Magnetic Field, *Egyptian Journal of Petroleum*, Volume 17, pp. 1029–1033
- Min, P.H., Shahbaz, K., Rashmi, W., Mjalli, F.S., Hashim, M.A., Alnashef, I.M., 2015. Removal of Residual Catalyst from Palm Oil-based Biodiesel Using New Ionic Liquids Analogous. *Journal of Engineering Science and Technology*, Volume 4(4), pp. 35–49
- Nieuwelink, A.E., Velthoen, M.E., Nederstigt, Y.C., Jagtenberg, K.L., Meirer, F., Weckhuysen, B.M., 2020. Single Particle Assay to Determine Heterogeneities within Fluid Catalytic Cracking Catalysts. *Chemistry-A European Journal*, Volume 26, pp. 8564–8554
- Oliveira, B.F.H.d., de-França, L.F., Fernandes-Corrêa, N.C., Ribeiro, N.F.D.P., Velasquez, M., 2021. Renewable Diesel Production from Palm Fatty Acids Distillate (PFAD) via Deoxygenation Reactions. *Catalysts*, Volume 11(9), pp. 1–16
- Onlamnao, K., Tippayawong, N., 2020. Organic Liquid Products from Cracking of Used Cooking Oils with Commercial Catalysts. *Chemical Engineering Transactions*, Volume 78, pp. 55–60
- Orazbayev, B., Kozhakhmetova, D., Wójtowicz, R. Krawczyk, J., 2020. Modeling of a Catalytic Cracking in the Gasoline. *Energies*, Volume 13(18), pp. 1–13
- Prabasari, I.G., Sarip, R., Rahmayani, S., Nazarudin, 2019. Catalytic Cracking of Used Cooking Oil Using Cobalt-impregnated Carbon Catalysts. *Makara Journal of Science*, Volume 23(3), pp. 162–168
- Rasyid, R., Prihartantyo, A., Mahfud, M., Roesyadi, A., 2015. Hydrocracking of Calophyllum inophyllum Oil with Non- Sulfide CoMo Catalysts. *Bulletin of Chemical Reaction Engineering and Catalysis*, Volume 10(1), pp. 61–69
- Rasyid, R., Sabara, Z., Ainun-Pratiwi, H., Juradin, R., Malik, R., 2018. The Production of Biodiesel from A Traditional Coconut Oil Using NaOH/ γ -Al₂O₃ Heterogeneous Catalyst. Makassar. In: IOP Conference Series: Earth and Environmental Science, Volume 175, p. 012025
- Sardi, B., Ningrum, R.F., Ardianyah, V.A., Qadariyah, L., Mahfud, M., 2022. Production of Liquid Biofuels from Microalgae Chlorella sp. via Catalytic Slow Pyrolysis. *International Journal of Technology*, Volume 13(1), pp. 147–156
- Senter, C., Mastry, M.C., Zhang, C.C., Maximuck, W.J., Gladysz, J.A., & Yilmaz, B., 2021. Role of Chlorides in Reactivation of Contaminant Nickel on Fluid Catalytic Cracking (FCC) Catalysts. *Applied Catalysis A: General*, Volume 611, p. 117987
- Singh, H. K. G., Yusup, S., Quitain, A. T., Abdullah, B., Ameen, M., Sasaki, M., Kida, T., Cheah, K. W., 2020. Biogasoline Production from Linoleic Acid via Catalytic Cracking over Nickel and Copper-doped ZSM-5 Catalysts. *Environmental Research*, Volume 186, p. 109616

- Thambiyapillaia, S., Ramanujam, M., 2021. An Experimental Investigation and Aspen HYSYS Simulation of Waste Polystyrene Catalytic Cracking Process for the Gasoline Fuel Production. *International Journal of Renewable Energy Development*, Volume 10(4), pp. 891–900
- Thangaraj, B., Solomon, P.R., Muniyandi, B., Ranganathan, S., Lin, L., 2019. Catalysis in Biodiesel Production. *Clean Energy*, Volume 3(1), pp. 2–23
- Trisunaryanti, W., Triyono. T., Ghoni, M.A., Fatmawati. D.A., Mahayuwati. P.N., Suarsih, E., 2020. Hydrocracking of Callophyllum Inophyllum Oil Employing Co and/or Mo Supported on γ -Al₂O₃ for Biofuel Production. *Bulletin of Chemical Reaction Engineering & Catalysis*, Volume 15 (3), pp. 743–751
- Ulfiati, R., Dhaneswara, D., Harjanto, S., Fatriansyah, J.F., 2022. Synthesis and Characterization ZSM-5 Based on Kaolin as a Catalyst for Catalytic Cracking of Heavy Distillate. *International Journal of Technology*, Volume 13(4), pp. 860–869
- Wahyono, Y., Hadiyanto, Budihardjo, M.A., Hariyono, Y., Baihaqi, R.A., 2022. Multifeedstock Biodiesel Production from a Blend of Five Oils through Transesterification with Variation of Moles Ratio of Oil: Methanol. *International Journal of Technology*, Volume 13(3), pp. 606–618
- Wako, F.M., Reshad, A.S., Bhalerao, M.S., Goud, V.V., 2018. Catalytic Cracking of Waste Cooking Oil for Biofuel Production Using Zirconium Oxide Catalyst. *Industrial Crops & Products*, Volume 118, pp. 282–289
- Wang, C., Tian, X., Zhao, B., Zhu, L., Li, S., 2019. Experimental Study on Spent FCC Catalysts for the Catalytic Cracking Process of Waste Tires. *Processes*, Volume 7(6), p. 335
- Widayat, W., Wicaksono, A.R., Firdaus, L.H., Okvitarini, N., 2016. Synthesis H-Zeolite Catalyst by Impregnation KI/KIO₃ and Performance Test Catalyst for Biodiesel Production. *In: IOP Conference Series: Materials Science and Engineering*, Volume 107(1), p. 012044
- Yu, H., Liu, Y., Liu, J., Chen, D., 2019. High Catalytic Performance of an Innovative Ni/Magnesium Slag Catalyst for The Syngas Production and Tar Removal from Biomass Pyrolysis. *Fuel*, Volume 254, p. 115622
- Zaher, F., Gad, M.S., Aly, S.M., Hamed, S.F., Abo-Elwafa, G.A., Zahran, H.A., 2017. Catalytic Cracking of Vegetable Oils for Producing Biofuel. *Egypt Journal Chemical*, Volume 60(2), pp. 291–300
- Zhang, Y., Li, Z., Wang, Z. Ji, Q., 2021. Optimization Study on Increasing Yield and Capacity of Fluid Catalytic Cracking (FCC) Units. *Processes*, Volume 9, p. 1497
- Zheng, Z., Lei, T., Wang, J., Wei, Y., Liu, X., Yu, F., Ji, J., 2019. Catalytic Cracking of Soybean Oil for Biofuel over γ -Al₂O₃/CaO Composite Catalyst. *Journal of The Brazilian Chemical Society*, Volume 30(2), pp. 359–370